



Mold growth and moss growth on tropical walls

Chameera Udawattha^{a,*}, Himahansi Galkanda^b, Isuri Shanika Ariyaratne^b, G.Y. Jayasinghe^b, Rangika Halwatura^a

^a Department of Civil Engineering, University of Moratuwa, Sri Lanka

^b Department of Agricultural Engineering, Faculty of Agriculture, University of Ruhuna, Sri Lanka

ARTICLE INFO

Keywords:

Intrinsic properties
Mold growth
Moss growth
Tropics
Walling material

ABSTRACT

The building envelop is generally considered as our third skin. Moss growth and mold growth are constraints which reduce the strength of the third skin. This study is aimed to analyze the effect of the mold growth and moss growth on different walling materials such as Brick, cement blocks, cement stabilized earth block, Cabook, Mud concrete blocks, Geo polymerized earth blocks walls and plastered walls with cement plaster and rough finish plaster in a tropical climate.

Organic matter, surface roughness, water absorption capacity, sorptivity and the capillary action of those walling materials were studied first. After which mold growth and moss growth were conducted in the real world controlled environment to accelerate the mold growth and moss growth. The growth rate and the strength reduction due to the effect of mold growth and moss growth were studied.

The results demonstrate that walling materials with high porous spaces have the high potential to grow moss and mold. The walling materials with the high organic matter also encourage moss and mold growth. Interestingly it was found that even though materials like mud concrete block and geo polymerized earth blocks have high organic matter, their less surface roughness helped to reduce the moss growth and mold growth. And also, plastering can emphatically reduce the speed of mold growth and moss growth.

1. Introduction

The tropical climatic condition is the worst climate condition for building materials [1] [2] [3] [4]. Because, the tropics consist of rain, sun, high humid wind etc. [5] [6] [3]. The idea of the wall and roof are to protect human beings from these environmental constraints [4] [5] [6]. Hence, the capacity confronts those environmental constraints by the roof and wall are very important [7] [8] [9]. Not only environmental constraints but also there are other effects due to those environmental constraints such as weather degradation, scaling off the materials, natural decay, mold growth and moss growth. Molds can be found everywhere and can grow on any material in the presence of moisture. The growth of the mold is due to the pores. When the pores land on building materials they start to reproduce all over the material. Mold can be found in indoor climate as well as the outdoor climate. But the most dangerous mold can be found in indoor produced series of health problems due to a particle size of the mold [10].

Moss growth is subject to outdoor environments except in case of a water leak, which can be found in indoor climates. Moss growth is a common phenomenon in tropical climatic conditions. Moss growth is accelerated due to the rainy weather and stabilized by the materials

property. For instant moss, brick is easily subjected to moss growth.

The effect and the growth rate of mold and moss are not properly studied in tropical climatic conditions (See Table 1). Tropical climatic condition is the most favorable climate for mold and moss growth. Therefore it is essential to understand the causes of mold and moss growth in tropical walling Material.

Bio receptivity is also an important indicator of the durability of the construction materials. Flooding, leaky roofs, building-maintenance or indoor-plumbing problems can lead to interior mold growth. Water vapor commonly condenses on surfaces cooler than the moisture-laden air, enabling mold to flourish [5]. This moisture vapor passes through walls and ceilings, typically condensing during the winter in climates with a long heating season. Floors over crawl spaces and basements, without vapor barriers or with dirt floors, are mold-prone. The “doormat test” detects moisture from concrete slabs without a sub-slab vapor barrier [6].

On the other hand, some of the Architects and landscape designers prefer to have moss-grown materials. This is due to the beauty of the materials after the moss growth. Most of the landscaping was done after the aging the materials into moss growth surfaces. The most popular techniques are to paint curd on walls which need to be covered with

* Corresponding author.

E-mail address: udawatthe@gmail.com (C. Udawattha).

Table 1
Previous studies done in different climatic conditions.

	Source	Year	Climate region	Construction Materials	Study method	Results
1	Dubosc [11]	2001	Humid Subtropical			Porosity has an impact on moss growth
2	Tran [12]	2014	Oceanic Climate		Accelerated growth test	Mold growth required 80–95% RH and mold growth depend on ambient temperature, exposure time, the type and surface conditions of building material
3	Vitinen [13]	2010	Warm Summer Continental	Mortar Building Materials and Wall Assemblies	Mold Index evaluation method	
4	Johansson [14]	2005	Warm Summer Continental	Building Materials	Natural inoculation protocol	Critical moisture condition for mold growth is approximately 75% and higher value for some materials
5	Hoang [15]	2010	Tropical Wet and Dry	Green Building Materials		Presence of organic matter in a building material and its equilibrium moisture content are more important predictors of fungal susceptibility
6	Safiuddin [16]	2017	Oceanic Climate	Concrete		Concrete structures damage due to moss and mold growth under field conditions and sealers and coating systems can be used to prevent moss and fungus growth
7	D'Orazio [17]	2014	Oceanic Climate	ETICS and Clay Bricks	Laboratory-accelerated growth test	Bio receptivity of building materials strongly affected by surface roughness and total porosity
8	Pranjic [18]	2015	Oceanic Climate	Building Stones	Artificial colonization experiments	Bio receptivity of building stones is influenced by intrinsic properties, environmental parameters and specific microclimatic parameters
9	Johansson [19]	2013	Warm Summer Continental	Building Materials	Laboratory test	There is a critical moisture level for mold growth on each building material
10	Ozolins [20]	2014	Warm Summer Continental	Plywood, Wooden Logs and Aerated Concrete		Moisture have a negative influence on the building constructions and vapor barrier effectively decrease the mold growth risk
11	Black [21]	2014	Continental Climate	Wood Frame Wall Assemblies	Laboratory – accelerated growth test	The presence of liquid water greatly reduced the time to germination, the amount of mold growth, and the rate of mold growth and the borate treatment of the plywood increased the time to germination significantly
12	Johansson [22]	2012	Warm Summer Continental	Building Materials	Laboratory test	Microbial growth can be minimized by selecting building material which is tolerant to the expected conditions and the resistance is differ with the material type
13	Fantucci [23]	2017	Mediterranean climate	Buildings		The fine insulation rendering coating have significant effect on the mold growth risk reduction
14	Moller [24]	2017	Oceanic Climate	Interior Surfaces	Laboratory Experiment	Dry building materials are more resistant to mold growth at high humid conditions for a limited time period and organic materials are more prone to mold growth
15	Wahab [25]	2013	Tropical Climate	Buildings	Condition survey method	A research is needed to study mold growth in tropical climate building and suggest a various causes of mold growth that need to be considered
16	Stefanowski [26]	2017	Oceanic Climate	Bio based construction and insulation products	Novel screening method	Chipboard was the most susceptible to mold growth and wool the least when in direct and indirect contact with agar
17	Johansson [27]	2014	Warm Summer Continental	Building materials	Laboratory test	Mold growth resistant building materials can be selected by determining the critical moisture level and the RH of the material
18	Setyono [28]	2012	Tropical Climate	Cement and Fly-ash Mixture	Laboratory test	Greater the fly-ash percentage of the mixture higher the resistance of moss growth
19	This [29]	2015	Oceanic Climate	Wooden Claddings	Laboratory test	Wind, building direction and temperature and RH variation with the time are effect on moss growth
20	Gradeci [30]	2017	Oceanic Climate	Timber Building Envelopes	Probabilistic-based approach as	The mold growth behavior is very sensitive to the decision of which parameters are considered, and consequently, attention is required when analyzing and interpreting the outcomes

moss. Therefore, the study of micrology is very important to reduce and increase the moss growth. Moss growth occurs due to the algae growth on walling materials. Algae is pioneer colonizer, who settle and grow on rough surfaces. The growth speed is encouraged by physical factors such as relative humidity, exposure to the wind, light etc. And the growth speed is encouraged by biotic factors such as the amount of nutrients available and bio receptivity.

The concept of bio receptivity is the ability of a material to be colonized by living organisms. And it considerably counts for the materials property such as materials porosity, surface roughness capillary actionability and the pH value of the material. Natural observations show that unplastered walls with high surface rough walling materials are bio receptive than plastered and painted outdoor walls. And also, plastering and painting shall reduce the (rain) water retention capacity. By improving the surface the bio-film formation can be reduced.

A bio-film is a web sort of formation covering the surface of the walling material. It's a complex microbial population embedded in the matrix. However, the walling materials can be damaged, scaled off by the bio-film formation. And this will eventually reduce the durability of the material. This is defined as biodeterioration. Biodeterioration and the damages due to bio filming on walling materials were tested and evaluated by series of accelerated growth tests. The growth and the growing speed were quantitatively determined to achieve the research objectives.

1.1. Objectives

The objectives of this study were to understand the moss growth and mold growth effect on different walling materials in a tropical climate like Sri Lanka. The tropical climate is a harsh climate for building materials. The most common walling materials in Sri Lanka and newly invented walling materials were subjected to this study. By determining the novel walling materials is an additional objective to determine the quality of novel walling materials.

The research was initiated to understand the effect of plaster and their strength of to reduce the moss growth and mold growth. But then it was realized that economically disadvantaged people in the country cannot afford the plastering. Instead, they are using paint the rough wall and use it in raw condition. Therefore, the extensive study was conducted with naked walling materials as well in order to optimize the mold growth effect on different walling materials in Sri Lanka. However, the effect of painting weather shielding and water proofing are covering wide varieties, therefore, for this study we omitted paint works, and painted walls.

In addition to the moss and mold growth analyses, aimed at evaluating the materials physical properties which accelerate the micro-algae coverage. This was done by evaluating and comparing materials properties. The study techniques included were new analytical approaches such as 3D scanning by using the 3D scanner.

1.1.1. Climate and weather condition

Sri Lanka is having high humid climate. This is due to the monsoon rain and the ocean belt surrounding the island. Not only monsoon, but there are many reasons to produce regional rain during the year. The impact of the rain accelerates the moss growth and mold growth [31] [32] [33]. The impact of high humid is also governed by the high temperature. The country is located near the equator. Therefore, the heat radiation comes at a degree of 5°. This is critical in some seasons when the day temperature goes beyond 35 °C and night temperature goes below 25 °C (see Fig. 1).

2. Phases, materials and methods

2.1. Phases

Experimental activities were split into three main phases: (i)

material properties tests (ii) moss growth test; and (iii) mold growth test shown in Fig. 2. In the first phase, materials were selected for the study and material properties were tested. Specimens of the selected materials were studied for their organic matter content, water absorption (W_a), total porosity, capillary action (as water absorption coefficient, A), pH value and surface roughness (as arithmetical mean roughness, R_a). In the second phase walling samples were constructed and moss growth under accelerated environmental conditions was assessed. In the final phase the specimens were prepared for the mold growth test and mold coverage was assessed by visual inspection.

2.2. Material properties tests

2.2.1. Material selection

The basal focus of this study is to understand the durability of walling materials in tropical climates. Therefore, the most common walling materials were selected for the study such as brick, cement block and Cabook [34] [35] [36]. In addition to that the greenest walling materials such as cement stabilized earth blocks mud concrete blocks [37] and fly ash stabilized blocks were selected [38]. And also, the most common technology is to plaster walls with river sand or plaster walls with Portland cement [39]. Therefore, another two materials such as Portland cement putty plastering and typical rough plastering were selected. Three samples of each material were tested for each intrinsic property. All the selected walling materials and their abbreviations are shown in Table 2.

2.3. Organic matter content

Organic matter content is an important characteristic for bio receptivity of the material. Organic matter content of the specimens was tested according to the ASTM D2974-00 test standards [40]. Materials were grinded and dried in an oven for 24 h' time at 100 °C temperature until no change of mass occurred. Oven dried samples were burned in a muffle furnace for 48 h at 440 °C temperature until no change of mass occurred. The weight of the samples was measured after samples were completely ashes to determine the ash content (%). Organic matter content was calculated using following equation (1).

$$\text{Organicmattercontent}(\%) = 100 - \text{Ashcontent}(\%) \quad (1)$$

2.4. Water absorption

Water is the main requirement for the bio receptivity [41]. Walling materials absorb water when they are immersed in water or subject to a high relative humidity environment [15]. Water absorption test was conducted to measure the relative amount of water absorbed by specimens. ASTM C272/C272M - 12 test standards [42] were used for the test. Specimens were dried in an oven for 24 h at 100 °C temperature. The specimens weight, length, width, and thickness were measured. Dried specimens were horizontally immersed in a water container for 24 h. Immersion specimens' weight was measured after removing surface water. Water absorption was calculated using following equation (2).

$$\text{Water absorption (gcm}^{-3}\text{)} = \frac{W - D}{V} \quad (2)$$

Where:

h = specimen height, cm
l = specimen length, cm
w = specimen width, cm
V = specimen volume = l × w × h, cm³
D = pre-immersion mass of the specimen, g
W = specimen mass after immersion and blotting, g

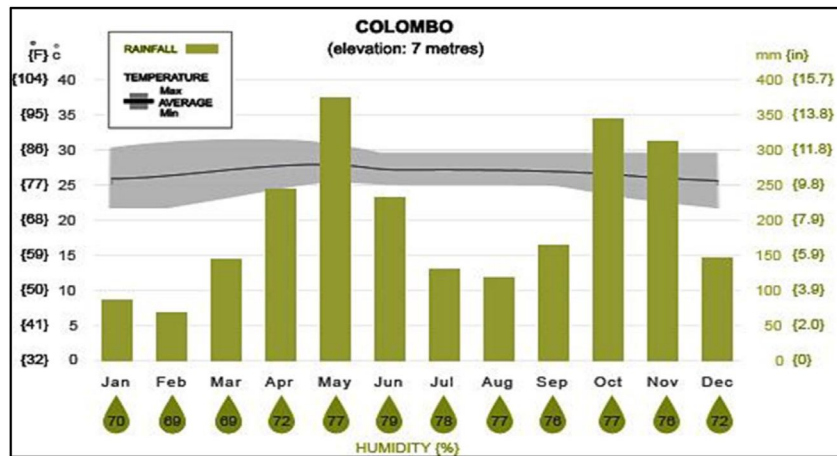


Fig. 1. Climate and weather condition variation in Colombo.

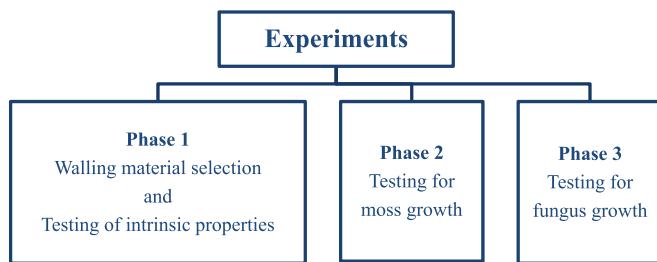


Fig. 2. Three phases of this experiment.

2.5. Total porosity

Porosity is the measure of the amount of void spaces present in the material. The high porosity increase water absorption capacity of the material [43]. The total porosity (ϕ) is defined by the ratio of the volume of void space (VV) to the total, or bulk volume of the material (VT). To test total porosity specimens were dried in an oven for 24 h at 100 °C temperature and specimens' weight, length, width and thickness were measured. Dried specimens were horizontally immersed in a water container for 24 h. Immersion specimens' weight was measured after removing surface water. Absorbed water volume (cm^3) by the material was calculated by dividing absorbed water mass (g) by the density of water (1 g/cm^3). Absorbed water volume was used as the volume of void space of the material. Total or bulk volume of the material was calculated using specimens' length, width and thickness measurements. Total porosity was calculated using following equation,

$$\text{Porosity}(\phi) = \frac{VV}{VT} \quad (3)$$

2.6. Capillary action

Capillary action test was conducted according to the ASTM C1585 - 13 test standards [44]. Specimens of each material were tested. Four side surfaces of the specimens were sealed by painting water base. The end of the specimen that will not be exposed to water was sealed using a loosely attached plastic sheet. Specimens were sealed to avoid evaporation from the specimen surfaces. Dimension of each specimen surface area, which is exposed to water, was measured and the mass of each specimen was measured. The supported device was placed at the bottom of the pan and the pan was filled with tap water and the water level was maintained at 1–3 mm above the top of the support device. The weight was recorded at the time periods according to the ASTM C1585 - 13 test standards. Capillary water absorption (I) was calculated by dividing the changing mass by cross-sectional area of the specimen and the density of water. Capillary water absorption coefficient was calculated using following equation (4).

$$I = \frac{mt}{(a \times d)} \quad (4)$$

Where,

I = absorption (mm)
 mt = the change in specimen mass (g)
 a = the exposed area of the specimen (mm^2)
 d = the density of water (gmm^{-3}) (0.001 gmm^{-3})

The initial rate of capillary water absorption ($\text{mms}^{-1/2}$) of the material was calculated as the slope of the line that is the best fit to I plotted against the square root of time ($\text{s}^{1/2}$).

Table 2
Specimens identification.

Walling material	Specimen code	Description
Cement Block	CB	Cement block is the cheapest walling materials made by using quarry dust and cement. These materials are available in hardware stores.
Brick	B	Brick is the most common walling material made by using clay. These materials are available in hardware stores.
Cement Stabilized Earth Block	CSEB	Cement Stabilized Earth Block is a novel green walling material. These materials are supply by specific suppliers.
Cabook Block	CAB	Cabook block is a naturally extracted walling material. These materials are available in hardware stores.
Mud Concrete Block	MCB	Mud Concrete Block is a novel green waling material introduce to tropics and they were casted.
Fly Ash Stabilized Earth Block	FSEB	Fly Ash Stabilized Earth Block is a novel green waling material introduced to tropics and they were casted.
Rough Cement Plaster	RCP	Rough Cement Plaster is a common wall plaster use for tropical walls. The plaster is made using cement, sand and water.
Cement Plaster	CP	Cement Plaster is a common wall plaster use in tropics. The plaster is made using cement and water.

2.7. pH value

pH value is determined by the concentration of the available hydrogen ions (H^+). pH value is measured on a negative logarithmic scale of hydrogen ion concentration. pH values vary from 0 to 14; pH values between 0 and 7 referred as acidic, values between 7 and 14 referred as basic or alkaline and pH 7 referred as neutral. Using the pH values, acidity or alkalinity of the walling materials can be determined which is effect on the bio receptivity. Biological growth on walling materials is sensitive to the acidity, alkalinity or neutral condition of the material. Fungus and moss species vary with the pH value; because some species prefer acidic conditions and some prefer alkaline conditions while rest of others prefers neutral conditions [45] [46].

pH value of walling materials were measured according to ASTM D 4972–95a test standards [47]. Walling materials were grinded to powder and dissolved in water. 10 g of the material was dissolved in 20 ml of distilled water. The mixture was thoroughly mixed and kept for 1 h and the pH values of the solutions were measured using a pH meter.

2.8. Surface roughness

Surface of a material is the boundary that separates the material from another material or substance. Surface roughness can be defined as the measure of the texture of a material surface [48]. Surface roughness of the material is directly effect on the bio receptivity of the material. Because surface roughness determine the surface area of the material and the amount of water retains on the material surface. When the surface roughness of the material is high material surface area is high; which can provide more surfaces for the bio receptivity. Also materials with high surface roughness value can hold more amount of water on the surface; which accelerate the bio receptivity of the material [17].

Surface roughness of the material can be quantified by the vertical deviations of a real surface from its ideal form. If the deviations are great the material surface is rough and if the deviations are small material surface is smooth. Surface roughness of each material was measured by 3D scanning the material sample as shown in Fig. 3. This is the latest technology to measure the surface roughness and quantified the surface roughness. There are two outputs can be taken by the 3Dscanner (i) Sectional profile of the material (ii) 3D profile of the material. And also we can evaluate the walling surface property after contamination.



Fig. 3. Studying surface roughness by using 3d scanner.

3. Moss growth test

3.1. Manufacturing of walling materials for the experiment

Most of the walling materials are available in Sri Lankan construction material market such as B, CB and CAB. Therefore, they were collected from a nearby store. But there are some novel walling materials such as CSEB which can only be found from a specific supplier. MCB and FSEB were casted because they can be produced at the lab scale according to the standards.

3.2. Construction of wall samples

An area with a shade and natural sun light was selected for wall samples construction. A concrete beam with 25 cm height from the ground was constructed as the base. A bituminous paint layer was painted on the top of the base to prevent capillary rise of groundwater through walling materials. Ground water can accelerate the moss growth [49]. 1 m × 1 m wall from bricks, cement blocks, CSEB, cabook blocks, MCB, FSEB and two additional brick walls were constructed on the beam with 50 cm gaps between each wall sample. One of the additional brick wall was plastered with rough cement plaster and other one is plastered with cement plaster. A small roof was mounted on the top of each wall sample to prevent rain water accumulation on the top of the wall (see Fig. 4).

Wall samples were constructed in a way that all walls can obtain same environmental conditions evenly. Sun direction, sun angle, shading, wind direction and all other environmental conditions were same for each wall sample.

3.3. Preparation and application of moss culture media

3.3.1. Materials

- Existing sample of moss (dead or alive)Water
- Buttermilk
- A blender
- A paintbrush

3.3.2. Culture media preparation

There are four basic moss types. They are sheet moss, cushion moss, haircap moss and rockcap moss. Cushion moss is the most common moss type on walls in tropics. Therefore, we used cushion moss which was grown on a brick wall as the existing moss sample. The common method [50] used to grow moss in landscape architecture was used to moss culture media preparation.

Equal amount of water and buttermilk were measured and blended. Existing moss was added to the mixture; moss: liquid mixture ratio at 1:4. All ingredients were blended until having a fine liquid mixture; until



Fig. 4. Wall samples.

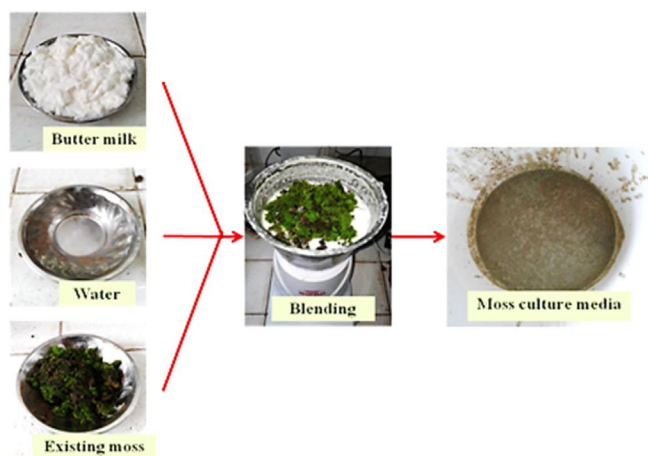


Fig. 5. Preparation of moss culture media.

existing moss cannot be separated. The mixture was painted as two layers on one surface of the each wall sample as 500 ml per square meter using a paintbrush. Wall samples were wetted with water twice a day to prevent walls from drying shown in Fig. 5.

3.4. Evaluation of moss growth

Moss growth area of each wall sample was measured weekly for period of three month (from 29th August 2017 to 2nd November 2017) time duration. Photos of walling materials were taken weekly to evaluate the color change due to the moss concentration variation with the time.

4. Mold growth test

4.1. Test specimens

Mold growth test was conducted according to the ASTM D3273-94 test standards [51] [52] [53]. This test evaluates the relative resistance of materials to surface mold and mildew growth in a severe environment over a 4-week period. The test utilizes a pan of moldy soil that continuously releases fungal spores in a high humidity, a warm temperature chamber, and challenging test pieces suspended above the soil for 28 days. Fungal growth is based on visual defacement using a 0 to 4 rating scale with 4 being completely covered with growth and 0 being clean. The walling samples of eight different materials were constructed according to the sample size of $150 \times 100 \times 7 \text{ mm}^3$.

4.2. Fungus culture

Potato dextrose agar media was prepared according to the procedure recommended in the Bacteriological Analytical Manual. 200 g unpeeled potatoes were sliced and boiled in 1 l distilled water for 30 min and filtered through cheesecloth; saving effluent, the potato infusion. 100 ml of the infusion and other ingredients were added into a flask and ingredients were mixed and boiled to dissolve. The media was gently agitated during the heating process by shaking the flask.

The flask with the media was capped loosely with cotton (see the Fig. 6). Media was sterilized in an autoclave for 15 min at 121°C temperature and 15 psi pressure. Glassware (petri dishes) was sterilized in an autoclave for 30 min at 121°C temperature and 15 psi pressure.

The flask was cooled for 20 min and the media was poured into sterilized petri dishes about one-half full. The petri dish was covered and allowed agar to solidify; see Fig. 7.

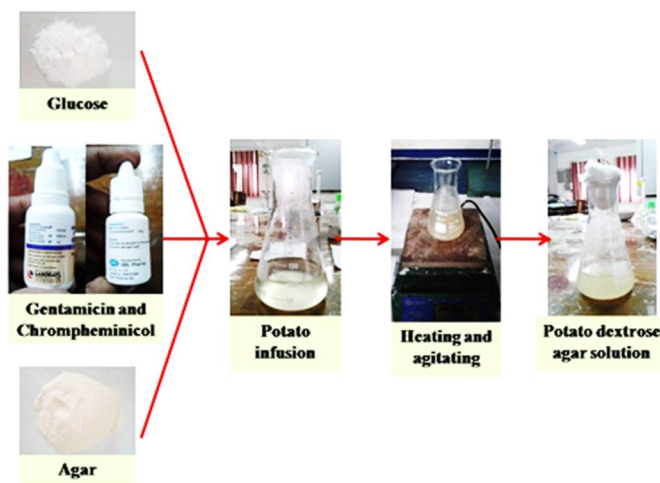


Fig. 6. Preparation of potato dextrose agar solution.



Fig. 7. Sterilization and solidification of agar media.

4.2.1. Culture transformation

Culture transformation is shown in. Inoculating loop was flamed and cooled to disinfection. Small quantity of the stock culture was picked up using the loop. The cover of the petri dish was raised gently, and the loop was touched to the top of the dish and streaked from side to side all the way to the bottom edge to have a zigzag pattern from edge to edge. The petri dish was incubated for 7 days.

4.2.2. Environmental chamber

A glass chamber shown in Fig. 8 was prepared as the environmental chamber. A mold growth media was prepared by mixing top soil, coir dust and compost according to the ratio of 2:1:1. The chamber was filled with the wetted growth media at 2.5 cm height. The chamber was equilibrated for 24 h in 32°C .

Prepared mold suspensions were evenly spreaded over the mold growing media and incubated for 14 days as shown in Fig. 9.

After 14 days the test specimens of three samples of each walling material were vertically hanged in the environmental chamber; from 50 mm above the media surface. The statistical design of completely randomized design (CRD) method was used to understand the mold growth rate. Environmental chamber conditions were controlled as; temperature at 27°C and relative humidity at 98%. The experiment was conducted from 31st August 2017 to 6th October 2017 (See Fig. 10).

4.2.3. Evaluation criteria

Mold growth on the surface of the specimens packed in the chamber shown in Figure was assessed weekly by visual inspection coupled with camera images. Mold covered surface area of specimens were rated according to the rating criteria of ASTM D3273-94; as in Table 3. After 4 weeks microscopic images of fungus were taken to identify the fungus species.

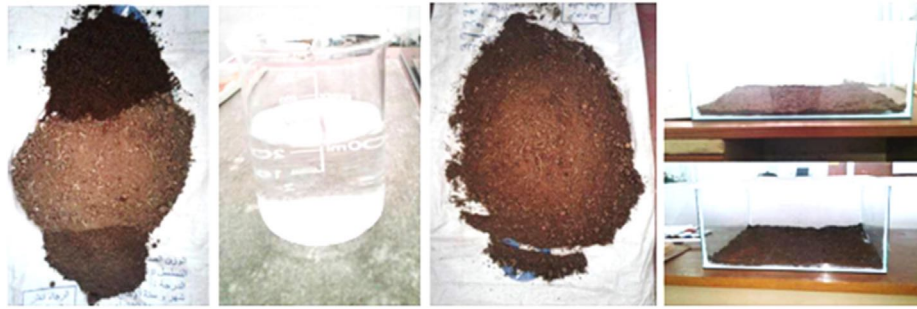


Fig. 8. Preparation of fungus growth media.

4.3. Data analysis

One-way ANOVA was carried out to identify the significant differences between tested eight materials considering their intrinsic properties, moss growth and fungus growth and Tukey Pairwise comparisons was carried out to indicate highly significant material. Calculated data of moss growth and fungus growth were subjected to a multiple regression analysis to identify the significant intrinsic properties. Significance of differences was defined at p -value < 0.05 . Minitab 18 data analysis software was used to perform the statistical analysis. Mean separation was done by using Tukey Pairwise.

5. Results and discussion

5.1. Intrinsic properties

Intrinsic properties of each material were tested and porosity, surface roughness, capillary water absorption, water absorption, organic matter content and pH values were measured as shown in Table 4.

5.1.1. Porosity of walling materials

Porosity of walling materials is shown in Table 4 and the values are in the range of 13.7%–34.5%. Mud Concrete Block has the highest porosity value and Fly Ash Stabilized Earth Block has the lowest. Porosity of Brick, Cement Stabilized Earth Block and Mud Concrete Block were not significantly different from each other and they were significantly different from other five materials. Porosity of Cement Block, Cabook Block, Fly Ash Stabilized Earth block, Cement Plaster and Rough Cement Plaster were not significantly different from each other and they were significantly different from other three materials.

5.1.2. Surface roughness of walling materials

Surface roughness of walling materials is shown in Table 4 and the values are in the range of $133.03\ \mu\text{m}$ – $2575.65\ \mu\text{m}$. Cabook Block has the highest surface roughness value and Brick has the lowest. All eight materials' surface roughness values are significantly different from each other.

5.1.3. Capillary water absorption of walling materials

Capillary action of walling materials is shown in Table 4 and the values are in the range of $0.082\text{mm s}^{-1/2}$ – $1.578\text{mm s}^{-1/2}$. Brick has the highest capillary water absorption and Cement Plaster has the lowest. All eight materials' capillary water absorption values are significantly

different from each other.

5.1.4. Water absorption of walling materials

Water absorption of walling materials is shown in Table 4 and the values are in the range of 0.14g cm^{-3} – 0.35g cm^{-3} . Mud Concrete Block has the highest porosity value and Fly Ash Stabilized Earth Block has the lowest. Porosity of Brick, Cement Stabilized Earth Block and Mud Concrete Block were not significantly different from each other and they were significantly different from other five materials. Porosity of Cement Block, Cabook Block, Fly Ash Stabilized Earth block, Cement Plaster and Rough Cement Plaster were not significantly different from each other and they were significantly different from other three materials.

5.1.5. Organic matter content of walling materials

Organic matter content of walling materials is shown in Table 4 and the values are in the range of 0.51%–10.36%. Cabook has the highest organic matter content and Brick has the lowest organic matter content. All eight materials' organic matter contents are significantly different from each other.

5.1.6. pH value of walling materials

pH values of walling materials are shown in Table 4 and the values are in the range of 7.81–11.63. Cement Plaster has the highest pH value and Cabook has the lowest pH value. All eight materials' pH values are significantly different from each other (See Table 5).

5.1.7. Comparison of moss growth area

Moss growth areas of eight wall samples were measured weekly as shown in Fig. 11. Cabook wall sample has the highest moss growth and no moss growth appeared on Cement Plaster and Rough Cement Plaster wall samples during the observed two months time period. Mud Concrete Block and Fly Ash Stabilized Earth Block wall samples have comparatively low moss growth.

5.1.8. Variation of moss growth with intrinsic properties

In the experiment, p values of pH value and capillary water absorption were lower than 0.05 ($P < 0.05$). pH value (P -value = 0.000) and capillary water absorption (P -value = 0.005) are the significant intrinsic properties of walling materials effect on the moss growth (Fig. 12); bio receptivity of walling materials is effected by intrinsic properties of the material [18] [54]. There is a positive correlation (Coef = +1288) between moss growth and capillary water absorption



Fig. 9. Distribution of fungus suspension and incubation.



Fig. 10. Fungus test.

Table 3

Mold growth-rating criteria.

Rating	Mold coverage
0	No growth
1	0 - 10%
2	11 - 30%
3	31 - 60%
4	61 - 100%

Table 4

Intrinsic properties of walling materials.

	Porosity (f) (%)	Surface Roughness (R _a) (μm)	Capillary Action (l) (mm s ^{-1/2})	Water Absorption (g cm ⁻³)	Organic Matter Content (%)	pH Value
B	28.9 ^a	133.03 ^h	1.578 ^a	0.29 ^a	0.51 ^h	9.42 ^f
CB	17.8 ^b	1149.17 ^b	0.814 ^d	0.18 ^b	0.82 ^g	11.49 ^c
CSEB	28.8 ^a	292.1 ^c	0.832 ^c	0.29 ^a	4.02 ^e	8.6 ^g
CAB	15.1 ^b	2575.65 ^a	0.568 ^f	0.15 ^b	10.36 ^a	7.81 ^h
MCB	34.5 ^a	1147.67 ^c	1.196 ^b	0.35 ^a	4.76 ^d	10.95 ^c
FSEB	13.7 ^b	197.46 ^g	0.672 ^e	0.14 ^b	6.22 ^c	11.4 ^d
CP	14.9 ^b	208.71 ^f	0.082 ^b	0.15 ^b	8.45 ^b	12.28 ^a
RCP	15.3 ^b	890.62 ^d	0.352 ^g	0.15 ^b	2.23 ^f	11.63 ^b

(B = Brick, CB = Cement Block, CSEB = Cement Stabilized Earth Block, CAB = Cabook Block, MCB = Mud Concrete Block, FSEB = Fly-ash Stabilized Earth Block, CP = Cement Plaster, RCP = Rough Cement Plaster) ((n = 3), Means that do not share a same letter; along each column, are significantly different according to DMRT).

of the material and the correlation between moss growth and pH value is negative (Coef = -524.9) (see Fig. 12).

5.1.9. Comparison of moss growth

At the end of the two months moss growth on walling samples were different to each other as shown in Fig. 13. There was no moss grown on Cement Plaster and Rough Cement Plaster; Cement Plaster and Rough Cement Plaster is a successful moss growth preventive method on walls but it cannot be recommended due to the environmental impacts of cement production. A dense moss growth was observed on the Cabook wall sample. Comparatively thicker moss growth was observed on the Fly Ash Stabilized Earth Block wall samples.

5.2. Mold growth test results

5.2.1. Comparison of mold growth

Fungus growth height on the walling material samples were observed weekly and rated according to the rating criteria of ASTM D3273-94 as shown in Fig. 14.

Brick has the highest fungus growth and the cement stabilized earth block has comparatively low fungus growth as shown in Fig. 14. The test was conducted using dry specimens; the results can differ if the specimens were wet before the study, further study is required to study fungus growth on wet specimens.

5.2.2. Variation of fungus growth with intrinsic properties

In the experiment, p values of organic matter content, pH value and capillary water absorption were lower than 0.05 ($P < 0.05$). Organic matter content (P -value = 0.003), pH value (P -value = 0.001) and capillary water absorption (P -value = 0.000) are the significant intrinsic properties of walling materials effect on the fungus growth (Fig. 15); bio receptivity of walling materials is effected by intrinsic properties of the material [17] [18]. There is a positive correlation between fungus growth and intrinsic properties (organic matter content (Coef = +11.56), capillary water absorption (Coef = +217) and pH value (Coef = +26.61)) of the material.









































































Fig. 15 shows the results of intrinsic properties and the mold growth effect of different walling materials. The pH value shows significant impact on mold growth. According to literature, the pH content directly helps to enhance the mold growth. But on the other hand there are mold species accelerated the growth due to pH and some are discouraged by pH content. Fig. 15 clearly shows there is a positive relationship between capillary action and mold growth. The mold needs some moisture. Usually these walling materials are dry. But the connection to the ground can create water absorption from the bottom to the roof depending on the capillary capacity. Therefore, this finding is interesting the fact that water absorption and capillary action can increase the mold growth on walling materials. Mould growth required moisture for the growth on the material surface. Materials with high water holding capacity (high surface roughness value) supports mold growth. Materials with high surface roughness and low organic matter content facilitate mold growth rather than materials with low surface roughness and high organic matter content. Therefore the findings show that materials with smooth surfaces are more resistant to mold growth even though they contain high organic matter. But actually organic matter may cause the mold growth is the surface organic matter. However, the result doesn't show any significant relationship between organic matter and mold growth.

6. Conclusion

Walling materials are prone to fungus and moss growth under the tropical climatic conditions. Moss does not growth on cement plaster and rough cement plaster and the fungus growth is lower on cement plaster and rough cement plaster. Cement plaster and rough cement plaster protect walling materials from fungus and moss growth under tropical climatic conditions; cement plaster and rough cement plaster

Table 5

Comparison of color change of walling materials (photos were taken weekly representing the worst case on each wall).

	0 days	7 days (1 week)	14 days (2 weeks)	21 days (3 weeks)	28 days (4 weeks)	35 days (5 weeks)	42 days (6 weeks)	49 days (7 weeks)	56 days (8 weeks)
B									
CB									
CSEB									
CAB									
MCB									
FSEB									
CP									
RCP									

cannot be recommended as a sustainable solution due to the environmental impacts and high cost of cement usage.

Porosity of walling materials varied in the range of 13.7%–34.5%. Water absorption of walling materials varied in the range of 0.14gcm^{-3} – 0.35gcm^{-3} . Surface roughness of walling materials varied in the range of $133.03\text{ }\mu\text{m}$ – $2575.65\text{ }\mu\text{m}$. Capillary water absorption of walling materials varied in the range of $0.082\text{ mms}^{-1/2}$ – $1.578\text{ mms}^{-1/2}$. Organic

matter content of walling materials varied in the range of 0.51%–10.36%. pH values of walling materials varied in the range of 7.81–11.63.

Cabook is the most susceptible walling material to moss growth and fly ash stabilized earth block is the least susceptible to moss growth under tropical climatic conditions. Brick is the most susceptible walling material to fungus growth and cement stabilized earth block is the least

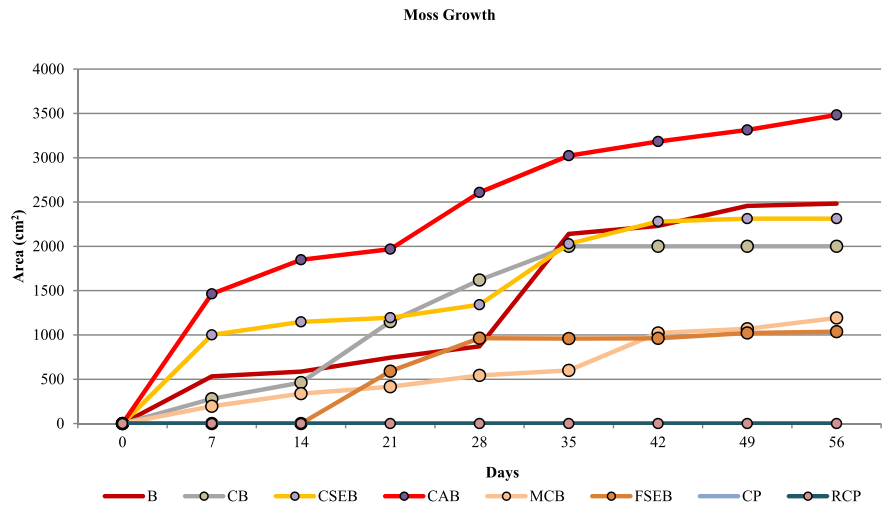


Fig. 11. Moss growth rate of walling materials.

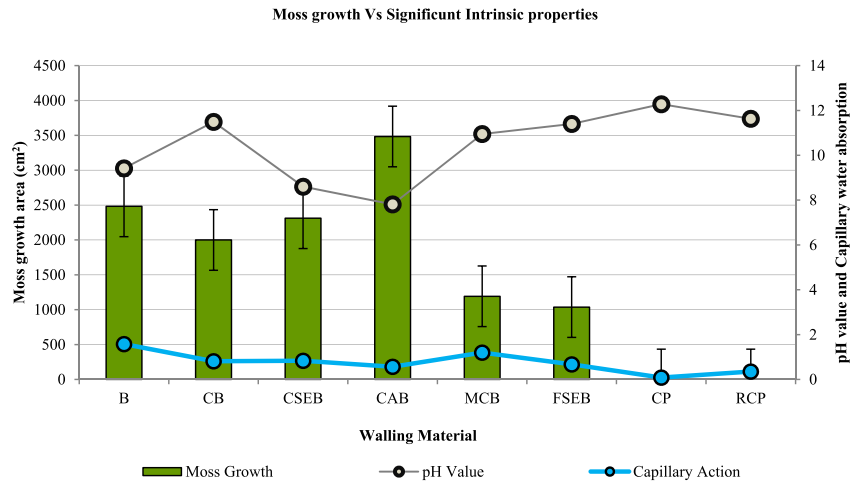


Fig. 12. Moss growth Vs. Significant Intrinsic properties.

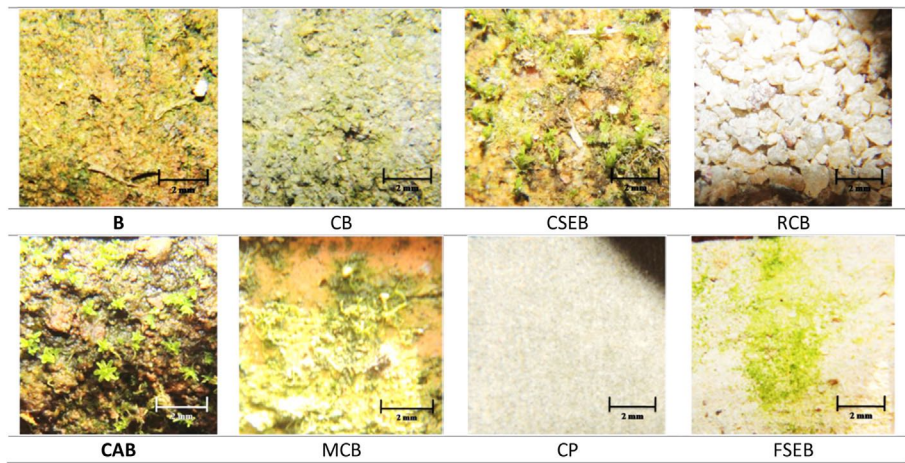


Fig. 13. Moss growth on walling materials after two months.

susceptible walling material to fungus growth.

Moss growth on walling material depends on the capillary water absorption and the pH value of the material. By increasing pH value and reducing capillary water absorption of the walling material moss growth resistant walling material can be produced.

Fungus growth on walling material depends on the capillary water

absorption, organic matter content and the pH value of the material. By reducing capillary water absorption, organic matter content and pH value of the walling material can produce fungus resistant walling material. Further research should be conducted to identify the major candidate for moss growth and mold growth in tropical climates and measures should be taken to mitigate the impact of them.

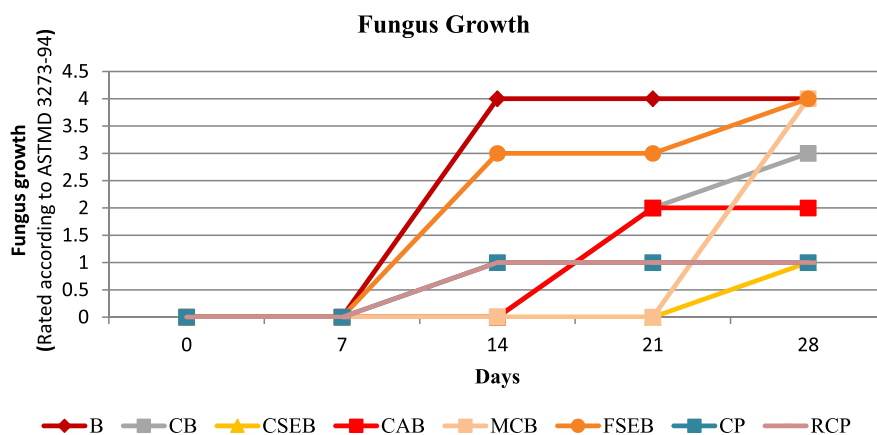


Fig. 14. Fungus growth of walling materials.

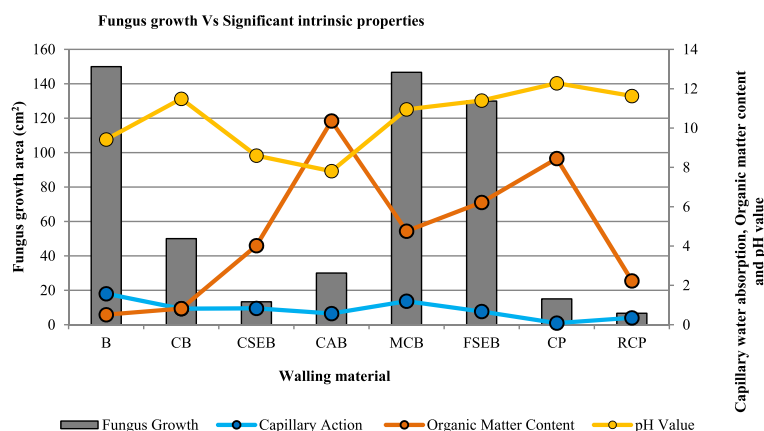


Fig. 15. Fungus growth Vs. Significant intrinsic properties.

Acknowledgment

This study is based on work supported by the NSF (National Science Foundation of Sri Lanka) grant number under RG/2017/EA & ICT/02. Any options, findings and conclusions or recommendation expressed in this material are those of the authors.

References

- [1] N. Gerald, R. Perera, Climate - Sensitive Urban Public Space: a Sustainable Approach to Urban Heat Island Mitigation in Colombo, Sri Lanka Climate, University of Moratuwa Sri Lanka, 2015, <http://dl.lib.mrt.ac.lk/bitstream/handle/123/12031/pre-text.pdf?sequence=1&isAllowed=y>.
- [2] R.U. Halwatura, M.T.R. Jayasinghe, Strategies for improved micro-climates in high-density residential developments in tropical climates, *Energy for Sustainable Development* 11 (2007) 54–65, [http://dx.doi.org/10.1016/S0973-0826\(08\)60410-X](http://dx.doi.org/10.1016/S0973-0826(08)60410-X) <https://www.sciencedirect.com/science/article/pii/S097308260860410X>.
- [3] H. Taha, Urban climates and heat islands: albedo, evapotranspiration, and anthropogenic heat, *Energy Build.* 25 (1997) 99–103, [http://dx.doi.org/10.1016/S0378-7788\(96\)00999-1](http://dx.doi.org/10.1016/S0378-7788(96)00999-1).
- [4] C. Udawaththa, R. Halwatura, Comparative study of embodied energy in different walling materials, *Proceedings of the International Forestry and Environment Symposium 2016*, Department of Forestry and Environmental Science, University of Sri Jayewardenepura, Sri Lanka, 2016, p. 2016 <http://journals.sjp.ac.lk/index.php/fesympo/article/view/3090>.
- [5] C. Udawaththa, R. Arooz, R. Halwatura, Energy content of walling materials- a comparison of mud concrete blocks, bricks cabook and cement blocks in tropics, *International Conference on Sustainable Built Environment 2016*, 2016 http://www.civil.mrt.ac.lk/conference/ICSBE_2016/ICSBE2016-54.pdf.
- [6] C. Udawaththa, R. Halwatura, The embodied energy and life cycle costing: a case study on basic dwellings in Sri Lanka, *National Green Conference 2016 at University of Kelaniya*, 2016, pp. 1–10.
- [7] M. D'Orazio, C. Di Perna, E. Di Giuseppe, M. D'Orazio, C. Di Perna, E. Di Giuseppe, The effects of roof covering on the thermal performance of highly insulated roofs in Mediterranean climates, *Energy Build.* 42 (2010) 1619–1627, <http://dx.doi.org/10.1016/j.enbuild.2010.04.004>.
- [8] R.U. Halwatura, Performance of insulated roofs with elevated outdoor conditions due to global warming, *Journal of Environmental Treatment Techniques* 2 (2014) 134–142.
- [9] R.U. Halwatura, Effect of turf roof slabs on indoor thermal performance in tropical climates: a life cycle cost approach, *Journal of Construction Engineering* 2013 (2013), <http://dx.doi.org/10.1155/2013/845158> e845158.
- [10] A. Arizzi, M. Brümmer, I. Martín-Sánchez, G. Cultrone, H. Viles, The influence of the type of lime on the hygric behaviour and bio-receptivity of hemp lime composites used for rendering applications in sustainable new construction and repair works, *PLoS One* 10 (2015), <http://dx.doi.org/10.1371/journal.pone.0125520>.
- [11] A. Dubosc, G. Escadeillas, P.J. Blanc, Characterization of biological stains on external concrete walls and influence of concrete as underlying material, *Cement Concr. Res.* 31 (2001) 1613–1617, [http://dx.doi.org/10.1016/S0008-8846\(01\)00613-5](http://dx.doi.org/10.1016/S0008-8846(01)00613-5).
- [12] T.H. Tran, A. Govin, R. Guyonnet, P. Grosseau, C. Loris, D. Damidot, O. Deves, B. Ruot, Influence of the intrinsic characteristics of mortars on their biofouling by pigmented organisms: comparison between laboratory and field-scale experiments, *Int. Biodeterior. Biodegrad.* 86 (2014) 334–342, <http://dx.doi.org/10.1016/j.ibiod.2013.10.005>.
- [13] H. Viitanen, J. Vinha, K. Salminen, T. Ojanen, R. Peuhkuri, L. Paajanen, L. Kimmo, Moisture and biodeterioration risk of building materials and structures, *J. Build. Phys.* 33 (2010) 201–224, <http://dx.doi.org/10.1177/1744259109343511>.
- [14] P. Johansson, I. Samuelson, A. Ekstrand-tobin, K. Mjornell, P.I. Sandberg, E. Sikander, *Microbiological growth on building materials – critical moisture levels, State of the art*, 11 (2005) 1–16.
- [15] C.P. Hoang, K.A. Kinney, R.L. Corsi, P.J. Szaniszlo, International Biodeterioration & Biodegradation Resistance of green building materials to fungal growth, *Int. Biodeterior. Biodegrad.* 64 (2010) 104–113, <http://dx.doi.org/10.1016/j.ibiod.2009.11.001>.
- [16] M. Safiuddin, Concrete damage in field conditions and protective sealer and coating systems, *Coatings* 7 (2017) 1–22, <http://dx.doi.org/10.3390/coatings7070090>.
- [17] M. D'Orazio, G. Cursio, L. Graziani, L. Aquilanti, A. Osimani, F. Clementi, C. Yéprémian, V. Lariccia, S. Amoroso, Effects of water absorption and surface roughness on the bioreceptivity of ETICS compared to clay bricks, *Build. Environ.* 77 (2014) 20–28, <http://dx.doi.org/10.1016/j.buildenv.2014.03.018>.
- [18] A.M. Pranjic, J. Mulec, T. Muck, A. Hlandnik, A. Mladenovic, *The bioreceptivity of building stone*, *Geophys. Res. Abstr.* 17 (2015).
- [19] P. Johansson, T. Svensson, A. Ekstrand-tobin, Validation of critical moisture conditions for mould growth on building materials, *Build. Environ.* 62 (2013) 201–209,

- <http://dx.doi.org/10.1016/j.buildenv.2013.01.012>.
- [20] A. Ozolins, A. Jakovics, Risks of mould growth in different building structures, International Conference Innovative Materials, Structures and Technologies, 2014, <http://dx.doi.org/10.7250/isconstrs.2014.19>.
 - [21] C. Black, J. Straube, Mould Growth Experiments of Full Scale Wood Frame Wall Assemblies, (2014).
 - [22] P. Johansson, A. Ekstrand-tobin, T. Svensson, G. Bok, Laboratory study to determine the critical moisture level for mould growth on building materials, Int. Biodeterior. Biodegrad. 73 (2012) 23–32, <http://dx.doi.org/10.1016/j.ibiod.2012.05.014>.
 - [23] S. Fantucci, F. Isaia, V. Serra, M. Dutto, Insulating coat to prevent mold growth in thermal bridges, Energy Procedia 134 (2017) 414–422, <http://dx.doi.org/10.1016/j.egypro.2017.09.591>.
 - [24] E.B. Møller, B. Andersen, C. Rode, R. Peuhkuri, Conditions for mould growth on typical interior surfaces, Energy Procedia 132 (2017) 171–176, <http://dx.doi.org/10.1016/j.egypro.2017.09.680>.
 - [25] A.N.S. Wahab, M.F. Khamidi, M.R. Ismail, An Investigation of Mould Growth in Tropical Climate Buildings, (2013), <http://dx.doi.org/10.1109/BEIAC.2013.6560139>.
 - [26] B.K. Stefanowski, S.F. Curling, G.A. Ormondroyd, A rapid screening method to determine the susceptibility of bio-based construction and insulation products to mould growth, Int. Biodeterior. Biodegrad. 116 (2017) 124–132, <http://dx.doi.org/10.1016/j.ibiod.2016.10.025>.
 - [27] P. Johansson, A. Ekstrand-tobin, G. Bok, An innovative test method for evaluating the critical moisture level for mould growth on building materials, Build. Environ. 81 (2014) 404–409, <http://dx.doi.org/10.1016/j.buildenv.2014.07.002>.
 - [28] P. Setyono, S. Suratman, Solidification coal fly Ash on A Textile factory as allelochemi to alternative Portland cement wall house anti-moss, Int. J. Adv. Sci. Eng. Inf. Technol. 2 (2012) 10–15, <http://dx.doi.org/10.18517/ijaseit.2.2.168>.
 - [29] T.K. Thiis, I. Burud, D. Kraniotis, L.R. Gobakken, The role of transient wetting on mould growth on wooden claddings, Energy Procedia 78 (2015) 249–254, <http://dx.doi.org/10.1016/j.egypro.2015.11.629>.
 - [30] K. Gradeci, N. Labonnote, B. Time, J. Kohler, A probabilistic-based approach for predicting mould growth in timber building envelopes: comparison of three mould models, Energy Procedia 132 (2017) 393–398, <http://dx.doi.org/10.1016/j.egypro.2017.09.641>.
 - [31] S. Gubanski, A. Dernfalk, S. Wallstrom, S. Karlsson, Performance and diagnostics of biologically contaminated insulators, 2006 IEEE 8th International Conference on Properties and Applications of Dielectric Materials, IEEE, 2006, pp. 23–30, <http://dx.doi.org/10.1109/ICPADM.2006.284109>.
 - [32] M.K. Matossian, Mold poisoning and population growth in england and France, 1750–1850, J. Econ. Hist. 44 (1984) 669–686, <http://dx.doi.org/10.1017/S0022050700032319>.
 - [33] E. Toxicology, Investigative study of biodeterioration of external sandcrete, Concrete Walls in Nigeria Investigative Study of Biodeterioration Sandcrete, Concrete Walls in Nigeria, 2016, <http://dx.doi.org/10.3923/rjet.2016>.
 - [34] C. Udawattha, R. Arooz, R.U. Halwatura, Energy content of walling materials- a comparison of mud-concrete blocks, bricks, cabook and cement blocks on tropics, 7th International Conference on Sustainable Built Environment, vol. 7, 2016, pp. 30–42 http://www.civil.mrt.ac.lk/conference/ICSBE_2016/ICSBE2016-54.pdf.
 - [35] C. Udawattha, R. Halwatura, Life cycle cost of different Walling material used for affordable housing in tropics, Case Studies in Construction Materials 7 (2017) 15–29, <http://dx.doi.org/10.1016/j.cscm.2017.04.005> <https://www.sciencedirect.com/science/article/pii/S2214509516300997>.
 - [36] C. Udawattha, R. Arooz, R. Halwatura, Manufacturing framework and cost optimization for building mud concrete blocks (MCB), Mobilization Modern Technologies for Sustainable Development in Asia, 2016, p. 112.
 - [37] C. Udawattha, H. Galabada, R. Halwatura, Mud concrete paving block for pedestrian pavements, Case Studies in Construction Materials 7 (2017) 249–262, <http://dx.doi.org/10.1016/J.CSCM.2017.08.005> <https://www.sciencedirect.com/science/article/pii/S221450951730058X>.
 - [38] C. Udawattha, R. Halwatura, Embodied energy of mud concrete block (MCB) versus brick and cement blocks, Energy Build. 126 (2016) 28–35, <http://dx.doi.org/10.1016/j.enbuild.2016.04.059>.
 - [39] D.J. Akers, J.M. Bannon, F.R. Day, R.W. Day, S.D. Edgett, D. Flickinger, G. p Gladfelter, Building Design and Construction Handbook, sixth ed., McGRAW-HILL, 2000.
 - [40] ASTM International, ASTM D2974–00, Standard Test Methods for Moisture, Ash, and Organic Matter of Peat and Other Organic Soils, West Conshohocken, (2000), <http://dx.doi.org/10.1520/D2974-00>.
 - [41] A. Jain, S. Bhadauria, V. Kumar, R.S. Chauhan, Biodeterioration of sandstone under the influence of different humidity levels in laboratory conditions, Build. Environ. 44 (2009) 1276–1284, <http://dx.doi.org/10.1016/j.buildenv.2008.09.019>.
 - [42] ASTM International, ASTM C272/C272M-12, Standard Test Method for Water Absorption of Core Materials for Sandwich, West Conshohocken, (2012), <http://dx.doi.org/10.1520/C0272.C0272M-12>.
 - [43] C. Udawattha, R. Halwatura, Thermal performance and structural cooling analysis of brick, cement block, and mud concrete block, Adv. Build. Energy Res. 0 (2016) 1–14, <http://dx.doi.org/10.1080/17512549.2016.1257438>.
 - [44] ASTM International, ASTM C1585–13, Standard Test Method for Measurement of Rate of Absorption of Water by Hydraulic-cement Concretes, West Conshohocken, (2013), <http://dx.doi.org/10.1520/C1585-13>.
 - [45] J.A. Grubb, H.S. Limaye, A.M. Kakade, Testing pH of concrete, Concr. Int. 29 (2007) 78–83.
 - [46] C. Udawattha, R. Arooz, R. Halwatura, New earth walling material: integrating modern technology into ancient mud wall, 7th International Conference on Sustainable Built Environment 2016, Kandy, Sri Lanka, 16th to 18th December 2016, 2016.
 - [47] ASTM, ASTM D 4972–01(2007)-Standard Test Method for PH of Soils, (2007), pp. 1–3.
 - [48] D.E. Aspnes, J.B. Theeten, F. Hottier, Investigation of effective-medium models of microscopic surface roughness by spectroscopic ellipsometry, Phys. Rev. B 20 (1979) 3292–3302, <http://dx.doi.org/10.1103/PhysRevB.20.3292>.
 - [49] Q.B. Bui, J.C. Morel, B.V. Venkatarama Reddy, W. Ghayad, Durability of rammed earth walls exposed for 20 years to natural weathering, Build. Environ. 44 (2009) 912–919, <http://dx.doi.org/10.1016/j.buildenv.2008.07.001>.
 - [50] How to Grow Your Own Moss | Apartment Therapy, (n.d.).
 - [51] S. Methods, Testing For Mold 0 (2005) 6–7.
 - [52] S.M. Luz, A.R. Gonçalves, A.P. Del'Arco, Mechanical behavior and microstructural analysis of sugarcane bagasse fibers reinforced polypropylene composites, Compos. Appl. Sci. Manuf. 38 (2007) 1455–1461, <http://dx.doi.org/10.1016/j.compositesa.2007.01.014>.
 - [53] D. Nrmrl, Microbial Resistant Test Method Development, (2014).
 - [54] E. Latif, M. Lawrence, A. Shea, P. Walker, Moisture buffer potential of experimental wall assemblies incorporating formulated hemp-lime, Build. Environ. 93 (2015) 199–209, <http://dx.doi.org/10.1016/j.buildenv.2015.07.011>.